


| | | |
|---|----------|------------|
|  Eskom | Standard | Technology |
|---|----------|------------|

Title: **Fabric Filter Plant Bag Standard** Unique Identifier: **240-53113965**

Alternative Reference Number: **N/A**

Area of Applicability: **Engineering**

Documentation Type: **Standard**

Revision: **3**




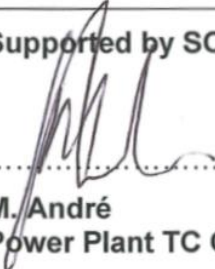
Total Pages: **46**

APPROVED FOR AUTHORISATION

☒ TECHNOLOGY ENGINEERING
DOCUMENT CENTRE ☎ x4962

Next Review Date: **October 2024**

Disclosure Classification: **CONTROLLED DISCLOSURE**

| | | |
|--|--|---|
| <p>Compiled by</p>  <p>.....</p> <p>E.M. Patel Senior Consultant: Air Pollution Control Date: <u>21/10/2019</u></p> | <p>Approved by</p>  <p>.....</p> <p>Y. Singh SCOT: AQC SC Chairperson Date: <u>31/10/2019</u></p> | <p>Authorised by</p>  <p>.....</p> <p>S. Govender General Manager: Plant Engineering (Acting) Date: <u>4/11/2019</u></p> |
| | | <p>Supported by SCOT TC</p>  <p>.....</p> <p>M. André Power Plant TC Chairperson Date: <u>05/11/2019</u></p> |

PCM Reference: **Perform Coal Power Plant Boiler Engineering 240-53459108**
SCOT Study Committee Number/Name: **SC03-01: Air Quality Control**

CONTENTS

| | Page |
|--|-----------|
| 1. INTRODUCTION | 5 |
| 2. SUPPORTING CLAUSES | 5 |
| 2.1 SCOPE | 5 |
| 2.1.1 Purpose | 5 |
| 2.1.2 Applicability | 5 |
| 2.2 NORMATIVE/INFORMATIVE REFERENCES | 5 |
| 2.2.1 Normative | 6 |
| 2.2.2 Informative | 6 |
| 2.3 DEFINITIONS | 6 |
| 2.3.1 Classification | 7 |
| 2.4 ABBREVIATIONS | 7 |
| 2.5 ROLES AND RESPONSIBILITIES | 7 |
| 2.6 PROCESS FOR MONITORING | 7 |
| 2.7 RELATED/SUPPORTING DOCUMENTS | 8 |
| 3. FABRIC FILTER PLANT BAG STANDARD | 8 |
| 3.1 POWER STATION UNIT BAG NUMBERS | 8 |
| 3.2 DOCUMENT CONTROL | 10 |
| 3.3 QUALITY ASSURANCE REQUIREMENTS | 10 |
| 3.4 MANUFACTURING AND DELIVERY PROGRAM | 12 |
| 3.5 SUPPLIER'S MANAGEMENT, SUPERVISION AND KEY PEOPLE | 12 |
| 3.6 PROVISION OF PERFORMANCE BONDS AND GUARANTEES | 12 |
| 3.7 BAG LIFE GUARANTEE | 13 |
| 3.8 SUPPLIER DUTY AND LOCAL CONTENT | 13 |
| 3.9 APPROVED SUPPLIERS | 14 |
| 3.9.1 Fibre suppliers | 14 |
| 3.9.2 Suppliers for Fabric Productions | 14 |
| 3.9.3 Local Bag Manufacturers | 14 |
| 3.9.4 Selection of Suppliers | 15 |
| 3.9.5 Technical Approval Process | 15 |
| 4. STATION SPECIFIC REQUIREMENTS | 16 |
| 4.1.1 Camden Power Station | 16 |
| 4.1.2 Hendrina Power Station | 17 |
| 4.1.3 Majuba Power Station | 18 |
| 4.1.4 Duvha Power Station | 19 |
| 4.1.5 Grootvlei Power Station | 20 |
| 4.1.6 Arnot Power Station | 21 |
| 4.1.7 Kusile Power Station | 22 |
| 4.1.8 Medupi Power Station | 23 |
| 4.1.9 Tutuka Power Station | 24 |
| 4.2 FILTER BAG FABRICATION | 25 |
| 4.2.1 PPS/PI SPECIFICATION FOR CAMDEN, DUVHA, GROOTVLEI, MEDUPI and (TUTUKA-tentative) | 25 |
| 4.2.1.1 Needle Felt Standard and Cloth Construction | 25 |
| 4.2.1.2 Scrim | 25 |
| 4.2.1.3 Batt – Cascade Construction | 25 |
| 4.2.1.3.1 Surface Layer (First Surface Layer – Dust Side) | 25 |
| 4.2.1.3.2 Support Layer (Second Inner Layer – Dust Side) | 26 |
| 4.2.1.3.3 Support Batt (Inner Layer – Clean Side) | 26 |
| 4.2.1.4 Cloth Construction | 26 |
| 4.2.1.5 Fabric Special Treatments | 26 |
| 4.2.1.6 Fabric Properties | 26 |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

| | |
|---|----|
| 4.2.2 PPS/PI SPECIFICATION FOR ARNOT | 26 |
| 4.2.2.1 Needle Felt Standard and Cloth Construction | 26 |
| 4.2.2.2 Scrim | 27 |
| 4.2.2.3 Batt – Cascade Construction | 27 |
| 4.2.2.3.1 Surface Layer (First Surface Layer – Dust Side) | 27 |
| 4.2.2.3.2 Support Layer (Second Inner Layer – Dust Side) | 27 |
| 4.2.2.3.3 Support Batt (Inner Layer – Clean Side) | 27 |
| 4.2.2.4 Cloth Construction | 27 |
| 4.2.2.5 Fabric Special Treatments | 27 |
| 4.2.2.6 Fabric Properties | 27 |
| 4.2.3 PAN/PI STANDARD FOR MAJUBA AND KUSILE | 28 |
| 4.2.3.1 Needle Felt Standard and Cloth Construction | 28 |
| 4.2.3.2 Scrim | 28 |
| 4.2.3.3 Batt - Cascade Construction | 28 |
| 4.2.3.3.1 Surface Layer (First Surface layer – Dust Side) | 28 |
| 4.2.3.3.2 Support Batt (Second Inner layer – Dust Side) | 28 |
| 4.2.3.3.3 Support Batt (Inner layer – Clean Side) | 28 |
| 4.2.3.4 Cloth Construction | 29 |
| 4.2.3.5 Fabric Special Treatments | 29 |
| 4.2.3.6 Fabric Properties | 29 |
| 4.2.4 PPS STANDARD FOR HENDRINA | 29 |
| 4.2.4.1 Needle Felt Standard and Cloth Construction | 29 |
| 4.2.4.2 Scrim | 29 |
| 4.2.4.3 Batt | 30 |
| 4.2.4.3.1 Surface Layer (First Surface Layer – Dust Side) | 30 |
| 4.2.4.3.2 Support Layer (Second Inner Layer – Dust Side) | 30 |
| 4.2.4.3.3 Support Batt (Inner Layer – Clean Side) | 30 |
| 4.2.4.4 Cloth Construction | 30 |
| 4.2.4.5 Fabric Special Treatments | 30 |
| 4.2.4.6 Fabric Properties | 30 |
| 4.2.5 GENERIC PAN/PI STANDARD FOR STATIONS TO BE RETROFITTED | 31 |
| 4.2.5.1 Needle Felt Standard and Cloth Construction | 31 |
| 4.2.5.2 Scrim | 31 |
| 4.2.5.3 Batt - Cascade Construction | 31 |
| 4.2.5.3.1 Surface Layer (First Surface layer – Dust Side) | 31 |
| 4.2.5.3.2 Support Batt (Second Inner layer – Dust Side) | 31 |
| 4.2.5.3.3 Support Batt (Inner layer – Clean Side) | 31 |
| 4.2.5.4 Cloth Construction | 32 |
| 4.2.5.5 Fabric Special Treatments | 32 |
| 4.2.5.6 Fabric Properties | 32 |
| 4.2.6 GENERIC PPS/PI SPECIFICATION FOR STATIONS TO BE RETROFITTED | 32 |
| 4.2.6.1 Needle Felt Standard and Cloth Construction | 32 |
| 4.2.6.2 Scrim | 32 |
| 4.2.6.3 Batt – Cascade Construction | 33 |
| 4.2.6.3.1 Surface Layer (First Surface Layer – Dust Side) | 33 |
| 4.2.6.3.2 Support Layer (Second Inner Layer – Dust Side) | 33 |
| 4.2.6.3.3 Support Batt (Inner Layer – Clean Side) | 33 |
| 4.2.6.4 Cloth Construction | 33 |
| 4.2.6.5 Fabric Special Treatments | 33 |
| 4.2.6.6 Fabric Properties | 33 |
| 4.3 TESTING AND INSPECTION REQUIREMENTS AND SAMPLE BAG MATERIALS | 34 |
| 4.3.1 Sample bag material | 34 |
| 4.3.2 Bag Testing Requirements | 34 |
| 4.3.2.1 Raw Materials | 34 |
| 4.3.2.2 Fabric Manufacture | 34 |
| 4.3.2.3 Bag Manufacture | 34 |
| 4.3.3 Labelling and Packaging of bags | 35 |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

| | |
|---|-----------|
| 4.3.4 Typical QCPs/ITPs | 36 |
| 4.4 DEVIATIONS FROM BAG MATERIAL STANDARD | 43 |
| 4.5 PRE-COATING OF BAGS..... | 44 |
| 4.6 SPARE BAGS | 44 |
| 5. AUTHORISATION..... | 45 |
| 6. REVISIONS | 45 |
| 7. DEVELOPMENT TEAM | 45 |
| 8. ACKNOWLEDGEMENTS | 46 |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

1. INTRODUCTION

Eskom utilizes needle felt fabric on its fabric filter plant (FFP) equipped operating units to curb particulate emissions. There are various types of material available to manufacture these filter bags from. Eskom has completed extensive research in order to understand which fabric filter media would function best in which operating environment.

This Standard was developed to ensure that a minimum standard is applied when procuring replacement filter bags for the respective power stations.

2. SUPPORTING CLAUSES

2.1 SCOPE

This document covers the minimum standard requirements for the purchase of replacement fabric filter plant filter media and bags, and serves to provide a consistent technical approach to the supply and delivery of fabric filter bags to all applicable Eskom operating units. Information regarding Polyphenylene sulphide (PPS), Polyimide (PI) and Homopolymer Polyacrylonitrile (PAN) materials as well as sample material requirements and plant guarantee requirements are contained herein.

2.1.1 Purpose

This Standard was developed to ensure that a minimum standard is applied when procuring replacement filter bags for the respective power stations.

2.1.2 Applicability

This document shall apply to the following Power Stations which have fabric filter plants installed:

- Arnot Power Station
- Camden Power Station
- Duvha Power Station (Units 1-3)
- Grootvlei Power Station
- Hendrina Power Station
- Majuba Power Station
- Medupi Power Station
- Kusile Power Station
- Tutuka Power Station (To be retrofitted with FFP's. Generic standards for Tutuka Power Station are included in this document. The specification could however change during the design of the fabric filter plant following finalisation of the process conditions and plant design.)

This document applies to all filter bags utilised at the above mention power stations, be it spare bags used for plant maintenance or routine replacement bags.

2.2 NORMATIVE/INFORMATIVE REFERENCES

Parties using this document shall apply the most recent edition/revision of the documents listed in the following paragraphs.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

2.2.1 Normative

- [1] 240-56242363 – Eskom Standard for Emissions Monitoring and Reporting.
- [2] 240-56244749 – Fabric Filter Plant Operational Procedure.
- [3] 240-48929482 – Tender Technical Evaluation Procedure
- [4] ISO 9001 – Quality Management System.
- [5] SABS ISO 14001, Framework of control to ensure that all SHE risks are considered along an auditable tract to ensure a successful outcome and continuous improvement.
- [6] 32-391 - Eskom Integrated Risk Management Procedure.
- [7] 39-7 - Reporting, Recording, Investigating, Costing and the Follow-up of SHE Incidents / Accidents.
- [8] Determination of Fabric Mass, Ash Mass and Cleanability of Fabric Filter Bags
: 240-119619889
- [9] Determination of the Permeability of Fabric Filter Bags to Air : 240-119619621
- [10] Tensile Properties of Fabrics: Determination of the Maximum Force of Fabric Filter Bags using the Grab Method : 240-119618026
- [11] Determination of Tearing Strength of Fabrics by the Tongue Method : 240-132338631
- [12] Determination of Dimensional Change in Fabric Filter Bags after Exposure to High Temperature
: 240-119619058Tensile Properties of Fabrics Determination of the Maximum Force of Fabric Filter Bags Using the Grab Method
- [13] 240-119619621 - Determination of Permeability of fabric filter bags
- [14] 240-105658000 Supplier Quality Management Specification
- [15] EN ISO 9073-2 – Methods of testing nonwovens: Determinations of thickness
- [16] 209-449 - Data Interpretation from the Textile Laboratory

2.2.2 Informative

- [17] EN 29073 – Methods of testing nonwovens: Determination of tensile strength and elongation
- [18] EN ISO 9237 – Textiles: Determination of air permeability
- [19] DIN 53887 – Frazier Differential Pressure air permeability tester
- [20] DIN 53861 – Testing of Textiles; Vaulting test and bursting test
- [21] UNI 8279/12 – Methods of testing nonwovens: Determination of dimensional change by heat
- [22] EN 12127 – Textiles and fabrics. Determination of Mass per unit area using small samples

2.3 DEFINITIONS

| Definition | Description |
|------------|---|
| Warp | Machine direction (MD) |
| Weft | Cross-machine direction or cross-direction (CD) |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

2.3.1 Classification

Controlled Disclosure: Controlled Disclosure to External Parties (either enforced by law, or discretionary).

2.4 ABBREVIATIONS

| Abbreviation | Description |
|--|--|
| °C | Degrees Celsius |
| dtex | Decitex |
| FFP | Fabric Filter Plant |
| g/m ² | Gram per square meter |
| g/Nm ³ | Gram per normal cubic meter (normalised to 10% O ₂ on a dry basis at 101.325 kPa & 0 °C) |
| K | Kelvin |
| kPa | Kilo Pascal |
| m ³ /m ² /minute | Cubic meter per square meter per minute |
| Max | Maximum |
| MCR | Maximum Continuous Rating |
| mg/Nm ³ | Milligram per normal cubic meter (normalised to 6% O ₂ on a dry basis at 101.325 kPa & 0°C) |
| Min | Minimum |
| mm | Millimeter |
| N/cm | Newton per centimetre |
| Nm ³ | Normal cubic meter (normalised to 6% O ₂ on a dry basis at 101.325 kPa & 0 °C) |
| O ₂ | Oxygen |
| Pa | Pascal |
| PAN | Polyacrylonitrile |
| PI | Polyimide (P84 ®) |
| PPS | Polyphenylene sulphide |
| QA | Quality Assurance |
| QC | Quality Control |

2.5 ROLES AND RESPONSIBILITIES

It is the responsibility of the System Engineer to ensure that the Standard is included in any purchase for filter bags at their respective stations, be it spare bags for maintenance purposes or full replacement bag sets. The System Engineer also need to ensure that the stores description of the bags reflect the latest version of this standard.

2.6 PROCESS FOR MONITORING

It is the System Engineers responsibility to ensure that all fabric intended for use are sampled and issued to the Eskom RT&D laboratory for analysis, following the process below

Step 1: Bag Order Placed and data sheet signed off

Step 2: Suppliers Laboratory Results received

Step 3: Fabric and Scrim Sample received (with transmittal sheet)

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

Step 4: Sample analysed by RT&D

Step 5: RT&D analysis report issued

Step 6: Supplier given feedback on sample analysis.

Step 7: Install bags and evaluate bag performance every 3 000 hours

2.7 RELATED/SUPPORTING DOCUMENTS

None

3. FABRIC FILTER PLANT BAG STANDARD

The objectives for this document include:

- Providing a consistent technical approach to the supply and delivery of fabric filter bags to the stations in line with the terms and conditions of the applicable purchasing contract.
- Ensuring that Eskom accepts and receives the right quality filter bags which will operate reliably and efficiently throughout their intended life.
- Sustaining and improving the power station's particulate emission performance.
- Ensuring the application, implementation and development of appropriate filter bag design, manufacturing and testing techniques.
- Developing performance standards which support the Eskom's reliability and optimised availability targets.
- Ensuring that suppliers shall provide adequate resources and engineering capability to support Eskom's objectives.

3.1 POWER STATION UNIT BAG NUMBERS

| Station | Unit No. | Installed No. of Bags | Recommended Min. No. of Bags to be Ordered (per full replacement set) |
|---------|----------|-----------------------|---|
| Arnot | 1 | 13 584 | 13 650 |
| | 2 | 13 584 | 13 650 |
| | 3 | 13 584 | 13 650 |
| | 4 | 10 934 | 11 000 |
| | 5 | 10 934 | 11 000 |
| | 6 | 10 934 | 11 000 |
| Camden | 1 | 9 616 | 9 650 |
| | 2 | 9 616 | 9 650 |
| | 3 | 9 616 | 9 650 |
| | 4 | 9 616 | 9 650 |
| | 5 | 9 616 | 9 650 |
| | 6 | 9 616 | 9 650 |
| | 7 | 9 616 | 9 650 |
| | 8 | 9 616 | 9 650 |
| | | | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

| | | | |
|-----------|----|--------|--------|
| Duvha *1 | 1 | 26 928 | 26 980 |
| | 2 | 26 928 | 26 980 |
| | 3 | 26 928 | 26 980 |
| | | | |
| | | | |
| Grootvlei | 1 | 8 832 | 8 880 |
| | 2 | 9 744 | 9 800 |
| | 3 | 9 744 | 9 800 |
| | 4 | 9 744 | 9 800 |
| | 5 | 8 832 | 8 880 |
| | 6 | 8 832 | 8 880 |
| | | | |
| Hendrina | 1 | 8 074 | 8 100 |
| | 2 | 8 832 | 8 900 |
| | 3 | 8 832 | 8 900 |
| | 4 | 8 832 | 8 900 |
| | 5 | 8 832 | 8 900 |
| | 6 | 7 984 | 8 050 |
| | 7 | 7 984 | 8 050 |
| | 8 | 7 984 | 8 050 |
| | 9 | 7 984 | 8 050 |
| | 10 | 7 984 | 8 050 |
| | | | |
| Majuba | 1 | 30 976 | 31 000 |
| | 2 | 30 976 | 31 000 |
| | 3 | 30 976 | 31 000 |
| | 4 | 32 512 | 32 550 |
| | 5 | 32 512 | 32 550 |
| | 6 | 32 512 | 32 550 |
| | | | |
| Medupi | 6 | 18 480 | 18 525 |
| | 5 | 18 480 | 18 525 |
| | 4 | 18 480 | 18 525 |
| | 3 | 18 480 | 18 525 |
| | 2 | 18 480 | 18 525 |
| | 1 | 18 480 | 18 525 |
| | | | |
| Kusile | 1 | 18 480 | 18 525 |
| | 2 | 18 480 | 18 525 |
| | 3 | 18 480 | 18 525 |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

| | | | |
|----------------------|---|--------|--------|
| | 4 | 18 480 | 18 525 |
| | 5 | 18 480 | 18 525 |
| | 6 | 18 480 | 18 525 |
| | | | |
| | | | |
| Tutuka ^{*2} | 1 | 20 160 | 20 250 |
| | 2 | 20 160 | 20 250 |
| | 3 | 20 160 | 20 250 |
| | 4 | 20 160 | 20 250 |
| | 5 | 20 160 | 20 250 |
| | 6 | 20 160 | 20 250 |
| | | | |

Notes:

*1 – As per the strategic report, Duvha will revert back to using the original number of bags to make sure that Duvha gets the maximum gas-to-cloth ratio. This is in-line with current best practise and also ensures sufficient margin against deteriorating coal and process conditions. It also assists in minimising the load losses incurred during on-load compartment outages.

*2 – Tutuka FFP retrofits expected to be completed between 2021 and 2026

3.2 DOCUMENT CONTROL

The Supplier shall have a documented management process that will describe the complete fabric and bag manufacturing process and will as a minimum describe how the following requirements will be met:

The Supplier shall carry out inspection at all stages of fabric and bag manufacture.

The Supplier shall repair defects revealed during the routine quality control checks, provided the Supplier demonstrates to the Purchaser's Representative satisfaction that such repairs do not, in any way, lessen the service life and performance of the material.

The Supplier will make provision for Purchaser's Representative to carry out random inspections during the fabric and bag manufacturing process.

During manufacture, as a minimum every 50th bag must be checked thoroughly using the approved bag inspection sheet. Records must be kept by the supplier and included in the data books.

The Supplier submits QA data sheets including test data. The data sheets must include, as a minimum, the results for measurements of the following parameters:

Raw Materials: Certificates of compliance and source of material and periodic batch tests of all components and raw materials.

Fabric Manufacture: Weight, Thickness, Air permeability, Breaking Strength and % elongation at 50 N/cm and at break (warp and weft directions), PI content and the Dimensional Stability (free shrinkage at 150 °C (PAN) or 180 °C (PPS) over 24 hrs, warp and weft).

Bag Manufacture: Length (under 5 kg tension), flat width and general compliance to Eskom Drawings.

All certificates are to reflect the Eskom order number.

3.3 QUALITY ASSURANCE REQUIREMENTS

The Supplier assures that they comply with the requirements contained within the ISO 9001/9002 quality system and the Eskom Supplier Quality Management Specification (QM-58) requirements.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

The generic Quality Plan as well as a proposed Inspection and Test Plan in strict compliance with the product standard are to be submitted with the Tender.

The Quality Assurance (QA) data sheets for fabric are provided at least three (3) week before the bag manufacturing commences.

The QA data sheets for bag manufacture will be provided with the bag delivery.

The Purchaser Representative will inspect the quality of the fabric according to the following Eskom Research and Strategy testing methods:

| METHOD | ESKOM NUMBER | EQUIVALENT STANDARD |
|--|-----------------------|-------------------------|
| Tearing Strength Determination of tearing strength of fabric by the tongue method | 240-119618026 | EN 29073-3 |
| Air Permeability | 240-119619621 | |
| Bursting Strength | | DIN 53861 |
| Breaking Strength | 240-119618026 | |
| Thermal Stability | | |
| P84 Content | | |
| Area Weight, Mass & Cleanability | 240-119619889 | EN 12127 |
| Thickness | | EN ISO 9073-2 |
| Micro analysis to determine the distinct cascaded layers of the cloth construction | To be advised | |
| pH Determination of aqueous extract from fabric filter bags | 240-119619455 | |
| - Determination of Fabric Mass, Ash mass and Cleanability of fabric filter bags | 240-119619889 | EN 12127 |
| - Determination of dimensional change in fabric filter bags after exposure to high temperature | 240-119619058 | UNI 8279/12 |
| Solubility of Polyimide(P84) in Polyacrylonitrile (PAN) 2 (11 2013) | Still to be validated | |
| Determination of the maximum force of fabric filter bags using the grab method | 240-119618026 | EN 29073-3 |
| Determination of Permeability of fabric filter bags to air | 240-11961962162P4002 | EN ISO 9237 / DIN 53887 |
| Solubility of Polyimide(P84) in Polyphenylene Sulphide (PPS) | 240-119618310 | |
| | | |

The Supplier can view and discuss these methods or other applicable testing methods prior to contract award in order to agree about their suitability with the Purchaser's Representative.

All raw materials (i.e. fibre, thread, snap bands, seals, etc.) must have certificates of compliance.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

The data books must include the details of the tags and numbers with complete traceability to the fabric slit width roll number.

3.4 MANUFACTURING AND DELIVERY PROGRAM

The Supplier provides manufacturing and delivery schedules. The Supplier delivers all bags to site as per the required delivery schedule.

The Supplier submits to the Purchaser's Representative the following documentation:

- Generic Quality Plan Included in Tender
- Proposed Inspection and Test Plan Included in Tender
- QA/QC procedure for approval Prior to manufacturing commencement
- QA data sheets for fabric manufacture for each batch one week before bag manufacturing starts
- QA data sheets for bags manufacture with bag delivery
- The Supplier compiles a Delivery Schedule in liaison with the Purchaser's Representative.
- The Supplier submits to the Purchaser's Representative the Delivery Schedule, Accepted Programme and subsequent revisions on hard copy, as well as a software copy. The software package is Microsoft compatible (e.g. MS Project etc.).

3.5 SUPPLIER'S MANAGEMENT, SUPERVISION AND KEY PEOPLE

The Supplier is to provide names of key people responsible for the project as requested by the project manager. The information should include contact details of the key personnel.

3.6 PROVISION OF PERFORMANCE BONDS AND GUARANTEES

The Supplier may be requested to provide a performance bond to ensure compliance to performance guarantees. The terms of the performance bond will be detailed in the Purchasing Contract. Below is an example of how a performance bond could be structured to ensure performance guarantee compliance.

Performance Bonds (Minimum requirements)

The amount of the performance bond is 5 (five) % of the Contract Value per Unit. The performance bond will be released as follows:

- 50 % will be released 104 weeks after sectional completion of the whole of the works.
- The remaining 50 % will be released at the end of the defects guarantee period.

Routine Spare Bags (if applicable):

- 50 % will be released 52 weeks after sectional completion of the whole of the works.
- The remaining 50 % will be released at the end of the defects guarantee period.

Spare Unit Bags (if applicable):

- 50 % will be released 104 weeks after sectional completion of the whole of the works.
- The remaining 50 % will be released at the end of the defects guarantee period.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

The Supplier will as part of the tender returnables, provide a written assurance from the Supplier's bank that the Performance Bond can and will be issued within 4 (four) weeks of Contract Award/Acceptance Letter Issued.

3.7 BAG LIFE GUARANTEE

The bag guarantee periods for the individual stations are as follows:

- Arnot PPS bags: minimum of 32 000 operating hours for Units 1 to 3 and 28 000 for Units 4 to 6 operating hours after installation.
- Duvha PPS bags: minimum of 36 000 operating hours after installation.
- Camden PPS bags: minimum of 30 000 operating hours after installation.
- Grootvlei PPS bags: minimum of 32 000 operating hours after installation
- Hendrina PPS bags: minimum of 38 000 operating hours after installation.
- Hendrina PAN bags: minimum of 34 000 operating hours after installation.
- Majuba PAN bags: minimum of 25 000 two-shifting operating hours after installation and/or a minimum of 32 000 base-load/load-following operating hours.
- Medupi PPS bags: minimum of 10 000 operating hours after installation.
- Kusile PAN bags: minimum of 15 000 operating hours after installation.
- Tutuka PPS bags: minimum of 36 000 operating hours after installation.
- All guarantee limitations are to be specifically stated in the tender submission. If viewed as unreasonable by the Client, these submissions will not be considered.
- The Client will factor limitations of guarantee into the life cycle evaluation of each offer, if required.

Note that the PPS and PAN referred to above, is for the predominant base fibre used in the material which could or could not be blended with other fibre types, such as PTFE and/or P84®.

3.8 SUPPLIER DUTY AND LOCAL CONTENT

3.8.1.1 The Supplier provides fabric filter bags in accordance with the Product Information and this Standard, including the design, testing and manufacturing of the fabric and the filter bags to suit the process standards and ensure the proper fitting of the bags onto the existing bag cages and tube plate.

3.8.1.2 The Supplier will ensure local production of the following components of the bags:

- Tubing and cutting to size of the fabric.
- Manufacturing of the top and bottom cuff and sock components.
- Cutting and assembling of the snap ring.
- Assembly of the completed bag including all stitching and thermo welding activities
- Fabric manufacturing unless a concession is obtained by the Supplier from the Department of Trade and Industry (DTI) and the Client

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

3.9 APPROVED SUPPLIERS

3.9.1 Fibre suppliers

The following products, components and suppliers are approved by Eskom. No other substitutes will be accepted and Eskom requires written assurance as such.

Products:

- Polyphenylene sulphide (PPS) – Trade Names: **Procon, Huvis, Torcon and Nexylene**,
- Polyimide (PI) – Trade Name: **P84**
- Homopolymer Polyacrylonitrile (PAN) – Trade Names: **Dolanit, and AKSA**

3.9.2 Suppliers for Fabric Productions

The following suppliers have been approved by Eskom for fabric productions (including the sourcing of component materials):

- Solaft Gosford Plant (Australia)
- Andrew Webron's Lancs Plant (United Kingdom)
- Beier Envirotec's Pinetown Plant (South Africa)
- BWF's Offingen Plant (Germany)
- Gutsche's Fulda Plant (Germany)
- Heimbach's Duren Plant (Germany)
- Testori's Milan Plant (Italy)
- Kayser's Einbeck Plant (Germany)
- Filtafelt's Rosslyn Plant (South Africa)
- Valmet's Ovar Plant (Portugal)

3.9.3 Local Bag Manufacturers

The following suppliers have been approved by Eskom to manufacture bags within the borders of South Africa:

- Beier Envirotec's Pinetown Plant
- Filtafelt's Rosslyn Plant
- GI Filtration's Centurion Plant
- Clear Edge's Robertsham Plant
- Environmental Dynamic's Nigel Plant
- Filter Pure's Kya Sand Plant (limited production capability)
- Envirox Filtration Technologies' Eastrand Plant

FFP Original Equipment Manufacturers (OEMs) such as Howden Projects, Actom, Alstom/GE, DB Thermal/Balcke-Durr/SPX, Hamon, Bateman, Steinmuller, etc. will be allowed to participate in a competitive tender process as long as the requirements contained in this document are adhered to.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

3.9.4 Selection of Suppliers

Eskom reserves the right to add and/or remove to the above list (3.9.1 to 3.9.3) solely at its discretion. No exception to Eskom's approved list will be accepted. Any additional/potential supplier to this list will require extensive testing to be undergone and after successful trial evaluation may be considered for inclusion.

3.9.5 Technical Approval Process

Through Eskom's Research Centre and Supplier Assessment Departments (QA), a comprehensive testing and evaluation program is followed to ensure that the products used are fit for purpose. The level of detail varies depending on which aspect of the supply value chain is being evaluated. The typical periods of assessments are described below:

Table: Typical Technical Approval Process Timeframes

| Supply Chain Step | Assessment Description | Typical Assessment Durations |
|-------------------------------------|---|--|
| Resin manufacturing | Can the manufacturer produce resin that can be used for fiber extruded and withstand the required process conditions. This development is typically done between the resin and fiber suppliers. | 18 to 24 months |
| Fibre extrusion | Can the resin be extruded for fiber and also spun into yarn. The fiber then undergoes extensive laboratory tests. | 18 to 24 months |
| Yarn spinning | Same evaluation as fiber extrusion. | 12 to 18 months |
| Non-woven needle felt manufacturing | Tests fabric in simulated flue gas conditions in the laboratory. Tests the fabric in actual plant environment for fatal flaws Test the fabric in actual plant environment for life cycle assessment | 2 to 3 months 6 to 12 months 18 to 30 months |
| Filter bag manufacturing | Assessment capability of bag producer to produce bags to the required quality, volumes and consistency. Test the final bag in actual plant environment for fatal flaws. | 3 to 6 months 3 to 6 months |

An updated list of approved suppliers can be obtained from the Purchaser's representative prior to an enquiry being issued. Consideration must be given by all stakeholders to the above timeframes in their project sourcing plans.

Furthermore, it must be noted that the Department of Trade and Industry (DTI) has designated the textile industry. As such, permission needs to be obtained from the DTI prior to the enquiry close date for the importation of any component related to the bag, i.e. fibers, yarns, threads, scrims, snap bands, seal rings, bags etc.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4. STATION SPECIFIC REQUIREMENTS

4.1.1 Camden Power Station

| | |
|--|---|
| Continuous operating temperature range (FFP): | • 120 °C to 170 °C |
| Temperature control set point: | • None |
| Gas volume: | • Maximum 490 Am ³ / s |
| Gas volume: | • MCR 462 Am ³ / s |
| Flue gas oxygen content: | • 3% - 15% |
| Filtration velocity with one cell isolated: | • Maximum 0,022 m/s |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |
| Estimated number of starts per boiler: | • 50 per year |
| Mode of Operation: | • Load following and two shifting |
| Material Selection: | • PPS/PI |
| Exclusions from standard material standard: | • None |
| | • |
| Bag drawing number | • 25.15/36898 |
| Bag length | • 8 meters |
| Bag diameter | • 127 mm equivalent (Howden Design) |
| Required operational hours (max number of bags failing during this period) | • 32 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.4 kPa (flange to flange @ MCR with one cell isolated) |
| <ul style="list-style-type: none"> • The bag will conform to the requirements of bag drawing no. 25.15/36898 Revision latest. • The snap band joint is to be riveted. • The snap band seal will be an endless felt strip type. • The longitudinal seam of the bag shall be triple stitched. • The stitching thread will be 100 % PPS or PTFE • The cuff and base (foot/sock) material will be off 100% PPS • It is the Supplier's responsibility to ensure that the bags fit correctly into the tube plate and cages. • Before bag manufacturing will commence the Supplier will provide a sample bag to the Purchaser Representative for evaluation and acceptance. • No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric for manufacture, following fabric tests done by the Purchaser's RT&D department. • The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis. | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.1.2 Hendrina Power Station

| | |
|--|---|
| Continuous operating temperature: | • 100 °C to 150 °C |
| Temperature control set point: | • None |
| Gas Volume at MCR: | • MCR 462 Am ³ / s |
| Filtration velocity (with all cells in services): | • Maximum 0,018 m/s |
| Filtration velocity (with one isolated): | • Maximum 0,021 m/s |
| Flue gas oxygen content: | • 3% - 8% |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |
| Estimate number of starts per boiler | • 30 per year |
| Mode of Operation | • Load following |
| Material Selection: | • PPS |
| Exclusions from standard material standard: | • No PI (First Surface layer – Dust Side): Material will not be blended with PI, PPS only. |
| Bag drawing number | • 25.15/36898 |
| Bag length | • 8 meters |
| Bag diameter | • 127 mm equivalent (Howden Design) |
| Required operational hours (max number of bags failing during this period) | • 32 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.4 kPa (flange to flange @ MCR with one cell isolated) |

- The Filter Bag Style is of the Howden type.
- The *Supplier* manufactures the bag according to the details shown on drawing no 25.15/36898.
- The snap band joint is to be riveted.
- The snap band seal will be an endless felt strip type.
- The longitudinal seam of the bag shall be triple stitched.
- The cuff and base (foot/sock) material will be of 100% PPS
- The stitching thread will be 100 % PPS or PTFE
- It is the *Supplier's* responsibility to ensure that the bags fit correctly into the tube plate and cages.
- Before bag manufacturing will commence the *Supplier* will provide a sample bag to the *Purchaser* for his evaluation and acceptance.
- No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric for manufacture following fabric tests done by the Purchaser's RT&D department.
- The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.1.3 Majuba Power Station

| | |
|---|---|
| Continuous operating temperature range (FFP): | • 100 °C to 150 °C |
| Temperature control set point: | • 125 °C |
| Gas volume: | • Maximum 1 553 Am ³ / s |
| Flue gas oxygen content: | • 3% - 15% |
| Filtration velocity with one cell isolated: | • Maximum 0,020 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0,018 m/s |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Load following and two shifting |
| Material Selection: | • PAN/PI |
| Exclusions from standard material standard: | • None |
| Bag drawing number | • 0.66/95371 (latest revision) |
| Bag length | • 7 meters |
| Bag diameter | • 127 mm equivalent (Howden Design) |
| Required operational hours (max number of bags failing during this period) | • 32 000 (5%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.3 kPa (flange to flange @ MCR with one cell isolated) |
| <ul style="list-style-type: none"> • The Filter Bag Style is of the Bateman Howden type. • The <i>Supplier</i> manufactures the bag according to the details shown in drawing nr 0.66/95371 revision latest. • The snap band joint is to be riveted. • The snap band seal will be an endless felt strip type. • The longitudinal seam of the bag shall be triple stitched. • The cuff and base (foot/sock) material will be off 100% Homopolymer PAN • The stitching thread will be PAN PPS or PTFE • It is the <i>Supplier's</i> responsibility to ensure that the bags fit correctly into the tube plate and cages. • Before bag manufacturing will commence the <i>Supplier</i> will provide a sample bag to the <i>Purchaser</i> for his evaluation and acceptance. • No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric manufacturing following fabric tests done by the Purchaser's RT&D department. • The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis. | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.1.4 Duvha Power Station

| | |
|--|---|
| Continuous operating temperature range (FFP): | • 100 °C to 150 °C |
| Gas volume: | • Maximum 1 553 Am ³ /s |
| Temperature control set point: | • None |
| Flue gas oxygen content: | • 3% - 15% |
| Filtration velocity with one cell isolated: | • Maximum 0,020 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0,018 m/s |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Base load |
| Material Selection: | • PPS/PI |
| Exclusions from standard material standard: | • None |
| Bag drawing number | • 0.57/48834 (latest revision) |
| Bag length | • 8 meters |
| Bag diameter | • 135 mm |
| Required operational hours (max number of bags failing during this period) | • 32 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.4 kPa (flange to flange @ MCR with one cell isolated) |
| <ul style="list-style-type: none"> • The <i>Contractor</i> manufactures the bag according to the details shown on drawing No 0.57/48834 Revision latest • The double circular base and the 100 mm wide reinforcing strip will be off 100% PPS. • The Filter Bag comprises of one end open with Stainless Steel snap band covered with an endless felt strips sewn into a 100% PPS woven false hem with 4 rows of stitching to fit cell plate. The other end is closed with double circular base with exterior base the filter fabric and the interior base 100% PPS) plus 100 mm wide reinforcing strip also from 100% PPS treated side outside. • The snap band joint is to be riveted. • The longitudinal seam of the bag shall be triple stitched. • The sewing thread will be 100% PPS or PTFE. • It is the <i>Supplier's</i> responsibility to ensure that the bags fit correctly into the tube plate and cages. • Before bag manufacturing will commence the <i>Supplier</i> will provide a sample bag to the <i>Purchaser</i> for his evaluation and acceptance. • No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric manufacturing following fabric tests done by the Purchaser's RT&D department. • The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis. | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.1.5 Grootvlei Power Station

| | |
|---|---|
| Continuous operating temperature range (FFP): | • 100 °C to 150 °C |
| Gas volume: | • Maximum 550 Am ³ /s |
| Temperature control set point: | • None |
| Flue gas oxygen content: | • 3% - 15% |
| Filtration velocity with one cell isolated: | • Maximum 0.020 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0.015 m/s |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Load following and two shifting |
| Material Selection: | • PPS/PI |
| Exclusions from standard material standard: | • None |
| Bag drawing number | • 0.19.46445 (latest revision) |
| Bag length | • 8 meters |
| Bag diameter | • 150 mm equivalent |
| Required operational hours (max number of bags failing during this period) | • 32 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.4 kPa (flange to flange @ MCR with one cell isolated) |
| <ul style="list-style-type: none"> • The <i>Contractor</i> manufactures the bag according to the details shown on drawing No 0.19.46445 Revision Latest • The double circular base and the 100 mm wide reinforcing strip will be off 100% PPS. • The Filter Bag detail comprises of a 8040 mm x 146 mm diameter bag with one end open with Stainless Steel snap band covered with a felt strip sewn into a woven false hem with 4 rows of stitching to fit cell plate 155 mm diameter x 5 mm thick. The other end is closed with double circular base with exterior base the filter fabric and the interior base 100% PPS plus 100 mm wide reinforcing strip also from 100% PPS with the treated side on the outside. • The snap band joint is to be riveted. • The longitudinal seam of the bag shall be triple stitched. • The stitching thread will be 100% PPS or PTFE • It is the <i>Supplier's</i> responsibility to ensure that the bags fit correctly into the tube plate and cages. • Before bag manufacturing will commence the <i>Supplier</i> will provide a sample bag to the <i>Purchaser</i> for his evaluation and acceptance. • No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric following fabric tests done by the Purchaser's RT&D department. • The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis. | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.1.6 Arnot Power Station

Process standards

| | |
|---|----------------------------------|
| Continuous operating temperature range (FFP): | • 110 °C to 175 °C |
| Temperature control set point: | • None |
| Gas volume per unit: | • Maximum 975 Am ³ /s |
| Flue gas oxygen content: | • 3% - 15% |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Base load |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |

Performance requirements

| | |
|--|---|
| Filtration velocity with one cell isolated: | • Maximum 0,020 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0,018 m/s |
| Material Selection: | • PPS/PI |
| Exclusions from standard material standard: | • None |
| | • |
| Bag drawing number | • 26.41.38198 (latest revision) |
| Bag length | • 8 meters |
| Bag diameter | • 135 mm |
| Required operational hours (max number of bags failing during this period) | • 32 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.4 kPa (flange to flange @ MCR with one cell isolated) |

- The *Contractor* manufactures the bag according to the details shown on drawing No 26.41.38198 Revision latest.
- The double circular base and the 100 mm wide reinforcing strip will be off 100% PPS.
- The Filter Bag detail comprises of a 8040 mm x 146 mm diameter bag with one end open with Stainless Steel snap band covered with a felt strip sewn into a woven false hem with 4 rows of stitching to fit cell plate 155 mm diameter x 5 mm thick. The other end is closed with double circular base with exterior base the filter fabric and the interior base 100% PPS plus 100 mm wide reinforcing strip also from 100% PPS treated side outside.
- The snap band joint is to be riveted.
- The longitudinal seam of the bag shall be triple stitched.
- The stitching thread will be 100% PPS or PTFE
- It is the *Supplier's* responsibility to ensure that the bags fit correctly into the tube plate and cages.
- Before bag manufacturing will commence the *Supplier* will provide a sample bag to the *Purchaser* for his evaluation and acceptance.
- No manufacturing of bags will commence prior to the *Purchaser's* representative receiving, analysing and releasing the fabric manufacturing following fabric tests done by the *Purchaser's* RT&D department.
- The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis.

CONTROLLED DISCLOSURE

4.1.7 Kusile Power Station

Process standards

| | |
|---|--|
| Continuous operating temperature range (FFP): | • 110 °C to 150 °C, controlled at 125 °C |
| Gas volume per unit: | • Maximum 1 250 Am ³ /s (excl. Attemperation air) |
| Flue gas oxygen content: | • 3% - 15% |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Base load |
| Inlet dust concentration: | • 25 – 70 g/Nm ³ |

Performance requirements

| | |
|--|---|
| Filtration velocity with one cell isolated: | • Maximum 0,020 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0,016 m/s |
| Material Selection: | • PAN/PI |
| | • |
| Exclusions from standard material standard: | • None |
| Bag drawing number | • Z0088504 (latest revision) |
| Bag length | • 8.24 meters |
| Bag diameter | • 160 mm |
| Required operational hours (max number of bags failing during this period) | • 30 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.2 kPa (flange to flange @ MCR with one cell isolated) |

- The *Contractor* manufactures the bag according to the details shown on drawing No Z0088504 Revision Latest and the cage drawing no. Z0101050 Revision Latest
- The double circular base and the 100 mm wide reinforcing strip will be off 100% Homopolymer PAN.
- The Filter Bag detail comprises of a 8240 mm x 160 mm diameter bag with one end open with Stainless Steel snap band covered with a felt strip sewn into a woven false hem with 4 rows of stitching to fit cell plate 167 mm diameter x 5 mm thick. The other end is closed with double circular base with exterior base the filter fabric and the interior base 100% Homopolymer PAN plus 100 mm wide reinforcing strip also from 100% Homopolymer PAN treated side outside.
- The snap band joint is to be riveted or induction spot welded
- The longitudinal seam of the bag shall be triple stitched.
- The stitching thread will be PAN PPS or PTFE.
- It is the *Supplier's* responsibility to ensure that the bags fit correctly into the tube plate and cages.
- Before bag manufacturing will commence the *Supplier* will provide a sample bag to the *Purchaser* for his evaluation and acceptance.
- No manufacturing of bags will commence prior to the *Purchaser's* representative receiving, analysing and releasing the fabric following fabric tests done by the *Purchaser's* RT&D department.
- The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis.

CONTROLLED DISCLOSURE

4.1.8 Medupi Power Station

Process standards

| | |
|---|------------------------------------|
| Continuous operating temperature range (FFP): | • 110 °C to 150 °C, |
| Gas volume per unit: | • Maximum 1 250 Am ³ /s |
| Flue gas oxygen content: | • 3% - 15% |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Base load |
| Inlet dust concentration: | • 25 – 70 g/Nm ³ |

Performance requirements

| | |
|--|---|
| Filtration velocity with one cell isolated: | • Maximum 0,020 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0,016 m/s |
| Material Selection: | • PPS/PI |
| Exclusions from standard material standard: | • None |
| Bag drawing number | • Z0088504 (latest revision) |
| Bag length | • 8.24 meters |
| Bag diameter | • 160 mm |
| Required operational hours (max number of bags failing during this period) | • 10 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.2 kPa (flange to flange @ MCR with one cell isolated) |

- The *Contractor* manufactures the bag according to the details shown on drawing No Z0088504 Revision Latest and the cage drawing no. Z0101050 Revision Latest.
- The double circular base and the 100 mm wide reinforcing strip will be off 100% PPS.
- The Filter Bag detail comprises of a 8240 mm x 160 mm diameter bag with one end open with Stainless Steel snap band covered with a felt strip sewn into a woven false hem with 4 rows of stitching to fit cell plate 167 mm diameter x 5 mm thick. The other end is closed with double circular base with exterior base the filter fabric and the interior base 100% PPS plus 100 mm wide reinforcing strip also from 100% PPS treated side outside.
- The snap band joint is to be riveted or induction spot welded.
- The longitudinal seam of the bag shall be triple stitched.
- The stitching thread will be 100% PPS or PTFE
- It is the *Supplier's* responsibility to ensure that the bags fit correctly into the tube plate and cages.
- Before bag manufacturing will commence the *Supplier* will provide a sample bag to the *Purchaser* for his evaluation and acceptance.
- No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric following fabric tests done by the Purchaser's RT&D department.
- The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis.

CONTROLLED DISCLOSURE

4.1.9 Tutuka Power Station

Process standards

| | |
|---|------------------------------------|
| Continuous operating temperature range (FFP): | • 110 °C to 175 °C |
| Gas volume per unit: | • Maximum 1 359 Am ³ /s |
| Flue gas oxygen content: | • 3% - 15% |
| Estimated number of starts per boiler | • 150 per year |
| Mode of Operation | • Base load |
| Inlet dust concentration: | • 25 – 50 g/Nm ³ |

Performance requirements

| | |
|--|---|
| Filtration velocity with one cell isolated: | • Maximum 0,016 m/s |
| Filtration velocity with all cells in-service: | • Maximum 0,015 m/s |
| Material Selection: | • PPS/PI |
| Exclusions from standard material standard: | • None |
| Bag drawing number | • To be confirmed (latest revision) |
| Bag length | • 10 meters |
| Bag diameter | • 150 mm |
| Required operational hours (max number of bags failing during this period) | • 36 000 (3%) |
| Expected emission limits | • 30 mg/Nm ³ |
| Maximum emission limits | • 50 mg/Nm ³ |
| Maximum pressure drop | • 2.4 kPa (flange to flange @ MCR with one cell isolated) |

- The *Contractor* manufactures the bag according to the details shown on drawing No (to be confirmed) Rev (latest).
- The top collar is constructed of material similar to that of the filter bag. The term “similar” means a material that has equal or greater strength and emission control capability of that of the bag material. A dual bead band is provided within the top collar for sealing the bag to the tubesheet.
- The snap band is stainless steel material joined by spot weld or stainless steel rivets.
- Each bag has dual bottom disks constructed of like material as that of the bag.
- The inside surface of the bags are singed to facilitate cage removal from the bag.
- The double circular base and the 100 mm wide reinforcing strip will be off 100% PPS.
- The Filter Bag detail comprises of a 10 000 mm x 150 mm diameter bag with one end open with Stainless Steel snap band covered with a felt strip sewn into a woven false hem with 4 rows of stitching to fit cell plate 155 mm diameter x 5 mm thick. The other end is closed with double circular base with exterior base the filter fabric and the interior base 100% PPS plus 100 mm wide reinforcing strip also from 100% PPS treated side outside.
- The snap band joint is to be riveted or induction spot welded.
- The longitudinal seam of the bag shall be triple stitched.
- The stitching thread will be 100% PPS or PTFE. The vertical seams should be triple needle type 401. The horizontal seams should be double needle type 301.
- It is the *Supplier's* responsibility to ensure that the bags fit correctly into the tube plate and cages.
- Before bag manufacturing will commence the *Supplier* will provide a sample bag to the *Purchaser* for his evaluation and acceptance.

CONTROLLED DISCLOSURE

- No manufacturing of bags will commence prior to the Purchaser's representative receiving, analysing and releasing the fabric following fabric tests done by the Purchaser's RT&D department.
- Should welded seams be considered, the following will apply. Welded seams includes a tensile pull test per DIN or ASTM demonstrating a failure of no less than the acceptance value of the non-welded seam area. A minimum of one sample is tested for each contract. This test is conducted prior to seaming any material on the project. Use of welded seam is not permitted without prior written acceptance from the Employer of the results of the tests.
- The Employer reserves the right to randomly remove the bag filter on the floor for bag compliance analysis.

4.2 FILTER BAG FABRICATION

4.2.1 PPS/PI SPECIFICATION FOR CAMDEN, DUVHA, GROOTVLEI, MEDUPI and (TUTUKA-tentative)

4.2.1.1 Needle Felt Standard and Cloth Construction

| | |
|---------------------------|--|
| Fabric construction: | Scrim supported needle felt |
| Fibre chemical name: | Polyphenylene sulfide (PPS) |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Fabric thickness: | Minimum 1.8 mm |
| Sides needled | Both |
| Sewing Thread | Polyphenylene sulfide (PPS) |
| Snap band | Riveted/Welded Stainless Spring Steel (Diameter to fit tube plate) |
| Cuff Seal (if applicable) | Endless Rontex Ring (PPS) |
| Cuff Material | Polyphenylene sulfide (PPS) |
| Foot/Sock Material | Polyphenylene sulfide (PPS) |

4.2.1.2 Scrim

| | |
|------------------|---|
| Construction: | The scrim will be woven from Polyphenylene sulfide (PPS) yarns. |
| Material: | Polyphenylene sulfide (PPS) |
| Yarn type: | Spun staple yarn and/or multifilament |
| Weight: | 175 -185 g/m ² before needling (Loom State) |
| Fibre Dimension: | 2.2 dtex |

4.2.1.3 Batt – Cascade Construction

4.2.1.3.1 Surface Layer (First Surface Layer – Dust Side)

Construction: The surface layer will be a blend of the following fibre materials and to be needled as a distinct surface layer.

| | |
|------------------|--|
| Material 1: | Polyimide (P84) |
| Fibre dimension: | 1.7 dtex Multilobal |
| Weight: | 45 - 55 g/m ² (Before Needling) |
| Material 2: | Polyphenylene sulfide (PPS) |
| Fibre dimension: | 1.7 dtex trilobal |
| Weight: | 55 - 45 g/m ² (Before Needling) |

CONTROLLED DISCLOSURE

4.2.1.3.2 Support Layer (Second Inner Layer – Dust Side)

Material: Polyphenylene Sulfide (PPS)
Fibre dimensions: 2.2 dtex
Weight: 125 – 135 g/m² (Before Needling)

4.2.1.3.3 Support Batt (Inner Layer – Clean Side)

Material: Polyphenylene Sulfide (PPS)
Fibre dimension: 2.2 dtex
Weight: 190 - 200 g/m² (Before Needling)

4.2.1.4 Cloth Construction

Fabric Construction: Scrim supported needle felt
Weight: 580 – 620 g/m² range, 600 g/m² average
Number of sides needed: Both sides

4.2.1.5 Fabric Special Treatments

Coatings: None
Heat Set: Yes, as Required by Supplier
Singeing: Yes, as Required by Supplier
Calendaring: Yes, as Required by Supplier

4.2.1.6 Fabric Properties

Air permeability: 7.6 – 10 m³/m²/minute @ 125 Pa

Elongation: Warp: max. 6% @ 50 N/cm
Weft: max. 8 % @ 50 N/cm

Bursting strength: min. 2800 kPa

Dimensional stability: (Free shrinkage at 180 °C) Warp: max. 1.5%
Dry heat for 24hrs) Weft: max. 1.5%

Tensile strength: Warp: min. 9 00 N/50mm
Weft: min. 1 200 N/50mm

4.2.2 PPS/PI SPECIFICATION FOR ARNOT**4.2.2.1 Needle Felt Standard and Cloth Construction**

Fabric construction: Scrim supported needle felt
Fibre chemical name: Polyphenylene sulfide (PPS)
Weight: 580 – 620 g/m² range, 600 g/m² average
Fabric thickness: Minimum 1.8 mm
Sides needed: Both
Sewing Thread: Polyphenylene sulfide (PPS)
Snap band: Riveted/Welded Stainless Spring Steel (Diameter to fit tube plate)
Cuff Seal (if applicable): Endless Rontex Ring (PPS)
Cuff Material: Polyphenylene sulfide (PPS)
Foot/Sock Material: Polyphenylene sulfide (PPS)

CONTROLLED DISCLOSURE

4.2.2.2 Scrim

| | |
|------------------|---|
| Construction: | The scrim will be woven from Polyphenylene sulfide (PPS) yarns. |
| Material: | Polyphenylene sulfide (PPS) |
| Yarn type: | Spun staple yarn and/or multifilament |
| Weight: | 175 -185 g/m ² before needling (Loom State) |
| Fibre Dimension: | 2.2 dtex |

4.2.2.3 Batt – Cascade Construction

4.2.2.3.1 Surface Layer (First Surface Layer – Dust Side)

Construction: The surface layer will be a blend of the following fibre materials and to be needled as a distinct surface layer.

| | |
|------------------|--|
| Material 1: | Polyimide (P84) |
| Fibre dimension: | 1.7 dtex Multilobal |
| Weight: | 45 - 55 g/m ² (Before Needling) |
| Material 2: | Polyphenylene sulfide (PPS) |
| Fibre dimension: | 1.7 dtex trilobal |
| Weight: | 55 - 45 g/m ² (Before Needling) |

4.2.2.3.2 Support Layer (Second Inner Layer – Dust Side)

| | |
|-------------------|--|
| Material: | Polyphenylene Sulfide (PPS) |
| Fibre dimensions: | 2.2 dtex |
| Weight: | 125 – 135 g/m ² (Before Needling) |

4.2.2.3.3 Support Batt (Inner Layer – Clean Side)

| | |
|------------------|--|
| Material: | Polyphenylene Sulfide (PPS) |
| Fibre dimension: | 2.2 dtex |
| Weight: | 190 - 200 g/m ² (Before Needling) |

4.2.2.4 Cloth Construction

| | |
|--------------------------|--|
| Fabric Construction: | Scrim supported needle felt |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Number of sides needled: | Both sides |

4.2.2.5 Fabric Special Treatments

| | |
|--------------|------------------------------|
| Coatings: | None |
| Heat Set: | Yes, as Required by Supplier |
| Singeing: | Yes, as Required by Supplier |
| Calendaring: | Yes, as Required by Supplier |

4.2.2.6 Fabric Properties

| | |
|--|---|
| Air permeability: | 60 l/dm ² /min (+/- 20%) at 200 Pa |
| Elongation: | Warp: max. 6% @ 50 N/cm Weft: max. 8 % @ 50 N/cm |
| Bursting strength: | min. 2800 kPa |
| Dimensional stability: (Free shrinkage at 180 °C | Warp: max. 1.5% |
| Dry heat for 24hrs) | Weft: max. 1.5% |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

Tensile strength:

Warp: min. 9 00 N/50mm

Weft: min. 1 200 N/50mm

4.2.3 PAN/PI STANDARD FOR MAJUBA AND KUSILE

4.2.3.1 Needle Felt Standard and Cloth Construction

| | |
|----------------------|--|
| Fabric construction: | Scrim supported needle felt |
| Fibre chemical name: | Polyacrylonitrile (PAN) |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Fabric thickness: | Minimum 1.8 mm |
| Sides needed: | Both |
| Sewing Thread: | Polyacrylonitrile (PAN) |
| Snap band: | Riveted/Welded Stainless Spring Steel (Diameter to fit tube plate) |
| Cuff Seal: | Endless Rontex Ring (PAN) |
| Cuff Material: | Polyacrylonitrile (PAN) |
| Foot/Sock Material | Polyacrylonitrile (PAN) |

4.2.3.2 Scrim

| | |
|------------------|---|
| Construction: | The scrim will be woven from Polyacrylonitrile (PAN) yarns. |
| Material: | Polyacrylonitrile (PAN) |
| Yarn type: | Spun staple yarn and/or multifilament |
| Weight: | 175 -185 g/m ² before needling (Loom State) |
| Fibre Dimension: | 2.2 dtex |

4.2.3.3 Batt - Cascade Construction

4.2.3.3.1 Surface Layer (First Surface layer – Dust Side)

Construction: The surface layer will be a blend of the following fibre materials and to be needled as a distinct surface layer.

| | |
|------------------|--|
| Material 1: | Polyimide (P84) |
| Fibre dimension: | 1.7 dtex multilobal |
| Weight: | 45 - 55 g/m ² (Before Needling) |
| Material 2: | Polyacrylonitrile (PAN) |
| Fibre dimension: | 1.7 dtex maximum |
| Weight: | 55 - 45 g/m ² (Before Needling) |

4.2.3.3.2 Support Batt (Second Inner layer – Dust Side)

| | |
|-------------------|--|
| Material: | Polyacrylonitrile (PAN) |
| Fibre dimensions: | 2.2 dtex |
| Weight: | 120 - 130 g/m ² (Before Needling) |

4.2.3.3.3 Support Batt (Inner layer – Clean Side)

| | |
|------------------|--|
| Material: | Polyacrylonitrile (PAN) |
| Fibre dimension: | 2.2 dtex |
| Weight: | 190 - 200 g/m ² (Before Needling) |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.2.3.4 Cloth Construction

| | |
|-------------------------|--|
| Fabric Construction: | Scrim supported needle felt |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Number of sides needed: | Both sides |

4.2.3.5 Fabric Special Treatments

| | |
|-------------|------------------------------|
| Coatings: | None |
| Heat Set: | Yes, as Required by Supplier |
| Singeing: | Yes, as Required by Supplier |
| Calandring: | Yes, as Required by Supplier |

4.2.3.6 Fabric Properties

| | |
|--|--|
| Air permeability: | 7.6 – 13 m ³ /m ² /minute @ 125 Pa |
| Elongation: | Warp: max. 4% @ 50 N/cm Weft: max. 6% @ 50 N/cm |
| Bursting strength: | min. 2800 kPa |
| Dimensional stability: (Free shrinkage at 150 °C dry heat for 24hrs) | Warp: max. 1.5% Weft: max. 1.5% |
| Tensile strength: | Warp: min. 8 00 N/50mm Weft: min. 8 00 N/50mm |

4.2.4 PPS STANDARD FOR HENDRINA

4.2.4.1 Needle Felt Standard and Cloth Construction

| | |
|----------------------|--|
| Fabric construction: | Scrim supported needle felt |
| Fibre chemical name: | Polyphenylene sulfide (PPS) |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Fabric thickness: | Minimum 1.8 mm |
| Sides needed | Both |
| Sewing Thread | Polyphenylene sulfide (PPS) |
| Snap band | Riveted/Welded Stainless Spring Steel (Diameter to fit tube plate) |
| Cuff Seal | Endless Rontex Ring (PPS) |
| Cuff Material | Polyphenylene sulfide (PPS) |
| Foot/Sock Material | Polyphenylene sulfide (PPS) |

4.2.4.2 Scrim

| | |
|------------------|---|
| Construction: | The scrim will be woven from Polyphenylene sulfide (PPS) yarns. |
| Material: | Polyphenylene sulfide (PPS) |
| Yarn type: | Spun staple yarn and/or multifilament |
| Weight: | 175 -185 g/m ² before needling (Loom State) |
| Fibre Dimension: | 2.2 dtex |

CONTROLLED DISCLOSURE

4.2.4.3 Batt

4.2.4.3.1 Surface Layer (First Surface Layer – Dust Side)

Construction: The surface layer will consist of PPS only

| | |
|------------------|--|
| Material 1: | Polyphenylene sulfide (PPS) |
| Fibre dimension: | 1.7 dtex trilobal |
| Weight: | 100 - 110 g/m ² (Before Needling) |

4.2.4.3.2 Support Layer (Second Inner Layer – Dust Side)

| | |
|-------------------|--|
| Material: | Polyphenylene Sulfide (PPS) |
| Fibre dimensions: | 2.2 dtex |
| Weight: | 125 – 135 g/m ² (Before Needling) |

4.2.4.3.3 Support Batt (Inner Layer – Clean Side)

| | |
|------------------|--|
| Material: | Polyphenylene Sulfide (PPS) |
| Fibre dimension: | 2.2 dtex |
| Weight: | 190 - 200 g/m ² (Before Needling) |

4.2.4.4 Cloth Construction

| | |
|--------------------------|--|
| Fabric Construction: | Scrim supported needle felt |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Number of sides needled: | Both sides |

4.2.4.5 Fabric Special Treatments

| | |
|--------------|------------------------------|
| Coatings: | None |
| Heat Set: | Yes, as Required by Supplier |
| Singeing: | Yes, as Required by Supplier |
| Calendaring: | Yes, as Required by Supplier |

4.2.4.6 Fabric Properties

| | |
|---|--|
| Air permeability: | 7.6 – 10 m ³ /m ² /minute @ 125 Pa |
| Elongation: | Warp: max. 6% @ 50 N/cm Weft: max. 8 % @ 50 N/cm |
| Bursting strength: | min. 2800 kPa |
| Dimensional stability: (Free shrinkage at 180 °C Dry heat for 24hrs) | Warp: max. 1.5% Weft: max. 1.5% |
| Tensile strength: | Warp: min. 9 00 N/50mm Weft: min. 1 200 N/50mm |

CONTROLLED DISCLOSURE

4.2.5 GENERIC PAN/PI STANDARD FOR STATIONS TO BE RETROFITTED

Note: This is the generic standard for stations to be retrofitted with FFP's where the flue gas temperature entering the FFP can be controlled to below 125° C.

4.2.5.1 Needle Felt Standard and Cloth Construction

| | |
|----------------------|--|
| Fabric construction: | Scrim supported needle felt |
| Fibre chemical name: | Polyacrylonitrile (PAN) |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Fabric thickness: | Minimum 1.8 mm |
| Sides needled: | Both |
| Sewing Thread: | Polyacrylonitrile (PAN) |
| Snap band: | Riveted/Welded Stainless Spring Steel (Diameter to fit tube plate) |
| Cuff Seal: | Endless Rontex Ring (PAN) |
| Cuff Material: | Polyacrylonitrile (PAN) |
| Foot/Sock Material | Polyacrylonitrile (PAN) |

4.2.5.2 Scrim

| | |
|------------------|---|
| Construction: | The scrim will be woven from Polyacrylonitrile (PAN) yarns. |
| Material: | Polyacrylonitrile |
| Yarn type: | Spun staple yarn and/or multifilament |
| Weight: | 175 -185 g/m ² before needling (Loom State) |
| Fibre Dimension: | 2.2 dtex |

4.2.5.3 Batt - Cascade Construction

4.2.5.3.1 Surface Layer (First Surface layer – Dust Side)

Construction: The surface layer will be a blend of the following fibre materials and to be needled as a distinct surface layer.

| | |
|------------------|--|
| Material 1: | Polyimide (P84) |
| Fibre dimension: | 1.7 dtex multilobal |
| Weight: | 45 - 55 g/m ² (Before Needling) |
| Material 2: | Polyacrylonitrile (PAN) |
| Fibre dimension: | 1.7 dtex maximum |
| Weight: | 55 - 45 g/m ² (Before Needling) |

4.2.5.3.2 Support Batt (Second Inner layer – Dust Side)

| | |
|-------------------|--|
| Material: | Polyacrylonitrile (PAN) |
| Fibre dimensions: | 2.2 dtex |
| Weight: | 120 - 130 g/m ² (Before Needling) |

4.2.5.3.3 Support Batt (Inner layer – Clean Side)

| | |
|------------------|-------------------------|
| Material: | Polyacrylonitrile (PAN) |
| Fibre dimension: | 2.2 dtex |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

Weight: 190 - 200 g/m² (Before Needling)

4.2.5.4 Cloth Construction

Fabric Construction: Scrim supported needle felt
 Weight: 580 – 620 g/m² range, 600 g/m² average
 Number of sides needed: Both sides

4.2.5.5 Fabric Special Treatments

Coatings: None
 Heat Set: Yes, as Required by Supplier
 Singeing: Yes, as Required by Supplier
 Calendering: Yes, as Required by Supplier

4.2.5.6 Fabric Properties

Air permeability: 7.6 – 13 m³/m²/minute @ 125 Pa
 Elongation: Warp: max. 4% @ 50 N/cm
 Weft: max. 6% @ 50 N/cm
 Bursting strength: min. 2800 kPa
 Dimensional stability: (Free shrinkage at 150 °C dry heat for 24hrs) Warp: max. 1.5%
 Weft: max. 1.5%
 Tensile strength: Warp: min. 8 00 N/50mm
 Weft: min. 8 00 N/50mm

4.2.6 GENERIC PPS/PI SPECIFICATION FOR STATIONS TO BE RETROFITTED

Note: This is the generic standard for stations to be retrofitted with FFP's where the flue gas temperature entering the FFP cannot be controlled to below 125° C.

4.2.6.1 Needle Felt Standard and Cloth Construction

Fabric construction: Scrim supported needle felt
 Fibre chemical name: Polyphenylene sulfide (PPS)
 Weight: 580 – 620 g/m² range, 600 g/m² average
 Fabric thickness: Minimum 1.8 mm
 Sides needed: Both
 Sewing Thread: Polyphenylene sulfide (PPS)
 Snap band: Riveted/Welded Stainless Spring Steel (Diameter to fit tube plate)
 Cuff Seal: Endless Rontex Ring (PPS)
 Cuff Material: Polyphenylene sulfide (PPS)
 Foot/Sock Material: Polyphenylene sulfide (PPS)

4.2.6.2 Scrim

Construction: The scrim will be woven from Polyphenylene sulfide (PPS) yarns.
 Material: Polyphenylene sulfide (PPS)
 Yarn type: Spun staple yarn and/or multifilament
 Weight: 175 -185 g/m² before needling (Loom State)
 Fibre Dimension: 2.2 dtex

CONTROLLED DISCLOSURE

4.2.6.3 Batt – Cascade Construction

4.2.6.3.1 Surface Layer (First Surface Layer – Dust Side)

Construction: The surface layer will be a blend of the following fibre materials and to be needed as a distinct surface layer.

| | |
|------------------|--|
| Material 1: | Polyimide (P84) |
| Fibre dimension: | 1.7 dtex Multilobal |
| Weight: | 45 - 55 g/m ² (Before Needling) |
| Material 2: | Polyphenylene sulfide (PPS) |
| Fibre dimension: | 1.7 dtex trilobal |
| Weight: | 55 - 45 g/m ² (Before Needling) |

4.2.6.3.2 Support Layer (Second Inner Layer – Dust Side)

| | |
|-------------------|--|
| Material: | Polyphenylene Sulfide (PPS) |
| Fibre dimensions: | 2.2 dtex |
| Weight: | 125 – 135 g/m ² (Before Needling) |

4.2.6.3.3 Support Batt (Inner Layer – Clean Side)

| | |
|------------------|--|
| Material: | Polyphenylene Sulfide (PPS) |
| Fibre dimension: | 2.2 dtex |
| Weight: | 190 - 200 g/m ² (Before Needling) |

4.2.6.4 Cloth Construction

| | |
|-------------------------|--|
| Fabric Construction: | Scrim supported needle felt |
| Weight: | 580 – 620 g/m ² range, 600 g/m ² average |
| Number of sides needed: | Both sides |

4.2.6.5 Fabric Special Treatments

| | |
|--------------|------------------------------|
| Coatings: | None |
| Heat Set: | Yes, as Required by Supplier |
| Singeing: | Yes, as Required by Supplier |
| Calendaring: | Yes, as Required by Supplier |

4.2.6.6 Fabric Properties

| | |
|--|--|
| Air permeability: | 7.6 – 10 m ³ /m ² /minute @ 125 Pa |
| Elongation: | Warp: max. 6% @ 50 N/cm Weft: max. 8 % @ 50 N/cm |
| Bursting strength: | min. 2800 kPa |
| Dimensional stability: (Free shrinkage at 180 °C | Warp: max. 1.5% |
| Dry heat for 24hrs) | Weft: max. 1.5% |
| Tensile strength: | Warp: min. 9 00 N/50mm Weft: min. 1 200 N/50mm |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.3 TESTING AND INSPECTION REQUIREMENTS AND SAMPLE BAG MATERIALS

4.3.1 Sample bag material

Eskom requires 1 (one) square meter (minimum) of sample fabric for every 10 000 m² of fabric produced. The certificates detailing full test results carried out by the supplier on the fabric and scrim to determine compliance with the standard should be included with the fabric sample.

Furthermore, Eskom requires an additional 4 square meters of fabric plus 2 square meters of the raw scrim per unit that will be removed during the bag manufacturing process for compliance evaluation (at random and at discretion). The provision and cost of this additional fabric must be included in the scope of supply in any contract.

The Employer reserves the right to randomly remove bag filters from the production line for bag compliance analysis.

Fabric that does not conform to the standard will be rejected and new replacement fabric that conforms to the standard will need to be produced.

Where cascaded fabric construction is specified, the Supplier will provide prove of the cascade effect by means of microscopic analysis of the completed fabric. This will be done for every 10 000 m² of fabric produced

4.3.2 Bag Testing Requirements

4.3.2.1 Raw Materials

Certificates of compliance, source of material and periodic batch tests of all components and raw materials will need to accompany material at all stages of production.

4.3.2.2 Fabric Manufacture

The following items will need to be verified according to the required limits as per section 3.1 and 3.2 depending on the bag material standard.

- Weight
- Thickness
- Air permeability
- Breaking Strength
- Percentage elongation at 50 N/cm and at break (warp and weft directions)
- P84® content (if included in bag specification)
- Dimensional Stability
- Microscopic analysis confirming cascade fabric construction.

4.3.2.3 Bag Manufacture

The length of the bag, flat width and compliance to bag drawing needs to be verified under a 50N load.

CONTROLLED DISCLOSURE

4.3.3 Labelling and Packaging of bags

Labels that identifies each bag with a colour and/or shape coded tag showing the batch and bag number sewn into the top outer cuff such that it may be linked to all relevant information including the name of any manufacturing supplier needs to be attached to newly manufactured bags. No repeatability of tags and numbers will be allowed.


The packaging needs to be clearly marked with the fabric type and order number. Any other relevant information pertaining to the particular shipment should also be marked. Each package contains approximately 10 to 15 bags to facilitate manual handling by one person.

All bags in each package needs to be packed in sealed non-transparent plastic bags. The packaging must clearly differentiate between routine spares bags and the complete spare unit bags.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.3.4 Typical QCPs/ITPs

| | | | | | | | | |
|---|--|---|--|--|--|--|--|--|
|  | | FILTER BAG TEST & INSPECTION REPORT | | | | Contract No 4600022655 | | |
| Title of the Contract | | The Manufacturing and Supply of Complete Set of Fabric Filter Bags for <u>Duvha Unit 3.</u> | | | | Filter Bag Drawing No. 0.57/48834 Rev 2 BA Internal Product Code: 44181034-1 BA ORDER No. 4500906504 | | |
| Control Codes | | (*) Y = Acceptance / X = Reject. | | | | (**) Measure | | |

| Ref. No. | Control Description | Control Code | Spec | Bag 1 | Bag 2 | Bag 3 | Bag 4 | Remarks |
|----------|---|--------------|---------------------------|-------------|-------|-------|-------|---------|
| 1 | BAG IDENTIFICATION TAG | | Sketch | | | | | |
| 2 | RIVET POSITION (TO BE OPPOSITE CUFF SEAM) | (*) | ✓ | | | | | |
| 3 | TOP CUFF WIDTH | (**) | 110mm +/- 2mm | | | | | |
| 4 | DISTANCE FROM EDGE TO 2nd ROW OF STITCHING (top cuff) | (**) | 45 - 50 mm | | | | | |
| 5 | TOP CUFF FIT - SNAP BAND | (*) | ✓ | | | | | |
| 6 | TOP CUFF SEAM RUN OFF - VISUAL | (*) | ✓ | | | | | |
| 7 | SEAM RUN-OFF - ALONG LENGTH - VISUAL | (*) | ✓ | | | | | |
| 8 | DISTANCE FROM EDGE TO SEAM - ALONG LENGTH | (*) | min 2mm | | | | | |
| 9 | FLAT MEASURE | T | (**) | 209 +/- 3mm | | | | |
| | | M | (**) | | | | | |
| | | B | (**) | | | | | |
| 10 | LONGITUDINAL SEAM OVERLAP | T | (**) | 13-17mm | | | | |
| | | M | (**) | | | | | |
| | | B | (**) | | | | | |
| 11 | BOTTOM REINFORCEMENT CUFF WIDTH | (**) | 140 +/- 3mm | | | | | |
| 12 | BOTTOM CUFF - BOTTOM EDGE TO 2nd ROW OF STITCHING | (**) | min 10mm | | | | | |
| 13 | BOTTOM CUFF - 2nd ROW TO 3rd ROW OF STITCHING | (**) | 8 -10mm | | | | | |
| 14 | BOTTOM CUFF - SNAPBAND | (**) | 20mm +/- 2mm | | | | | |
| 15 | LENGTH AT 50 N (5kg) | (**) | 8085 - 8115 | | | | | |
| 16 | CAGE FITMENT - PENETRATION INTO BOTTOM CUFF | (**) | 40 - 70mm (for info only) | | | | | |

| | | |
|--------------------------------------|--|-----------------------------|
| Person conducting inspection: | | Date of inspection: |
| Suppliers Name: | | Suppliers signature: |
| Notes / Remarks: | | |
| | | |
| | | |
| | | |
| | | |
| | | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

[illegible]

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

[illegible]

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

| | | | | QUALITY PLAN | | | | | | | | | | | | PROJECT : Duvha | | | | | | | |
|---------------------------------------|---|--|--|--------------------|---|---|---|----------------|---------------------|---|---|---|---|---|---|-----------------|------------------|------------------|------|---------|--|--|--|
| CLIENT : ESKOM DUVHA Unit 3 | | | | 1 = Beier Albany | | | | | V = Verify | | | | | Quality Plan Reference : Duvha 2009 Rev # : 0 | | | | | | | | | |
| CLIENT ORDER # : | | | | 2 = Eskom | | | | | H = Hold | | | | | Page # : Page 3 of 6 | | | | | | | | | |
| ITEM DESCRIPTION : FABRIC FILTER BAGS | | | | 3 = | | | | | W = Witness | | | | | Drawing # : 0.57/48834 Rev. 2 | | | | | | | | | |
| PRODUCT CODE : | | | | 4 = | | | | | S = Surveillance | | | | | CONTRACT # : | | | | | | | | | |
| SUPPLIER # : | | | | 5 = | | | | | R = Record | | | | | | | | | | | | | | |
| | | | | Hold or Witness by | | | | | Inspection Required | | | | | | | | | | | | | | |
| Op # | Operation Description | | | Reference Document | 1 | 2 | 3 | 4 | 5 | V | D | S | P | E | M | D | Accept Signature | Reject Signature | Date | Remarks | | | |
| | | | | | | | | | | I | I | T | E | L | A | O | | | | | | | |
| | | | | | | | | | | S | M | R | R | O | S | C | | | | | | | |
| | | | | | | | | | | N | E | M | N | S | | | | | | | | | |
| 4 | RECEIVING INSPECTION : | | | MCP | | | | | | | | | | | | | | | | | | | |
| | RECEIPT OF MATERIAL : | | | | | | | | | | | | | | | | | | | | | | |
| | Delivery documents are compared with Purchase Documents for compatibility . | | | | | | | | | X | | | | | | X | | | | | | | |
| | Material is visually checked for : | | | | | | | | | | | | | | | | | | | | | | |
| | ~ Type | | | | | | | | | X | | | | | | | | | | | | | |
| | ~ Quantity | | | | | | | | | X | | | | | | | | | | | | | |
| | ~ Transit damage | | | | | | | | | X | | | | | | | | | | | | | |
| | Certificate of Conformance are required for : | | | Eskom | | | | | | | | | | | | | | | | | | | |
| | ~ Pre-Slit Needlefelt | | | Spec | W | V | | | | | | | | | | X | | | | | | | |
| | ~ Snapband Stainless Steel | | | | W | V | | | | | | | | | | X | | | | | | | |
| | ~ Thread | | | | W | V | | | | | | | | | | X | | | | | | | |
| | ~ Seals | | | | W | V | | | | | | | | | | X | | | | | | | |
| | ~ Rivets | | | | W | V | | | | | | | | | | X | | | | | | | |
| | ~ Assembled Snapbands | | | | W | V | | | | | | | | | | X | | | | | | | |
| SUPPLIER APPROVAL : | | | | DATE | | | | ESKOM APPROVAL | | | | | | | | | | | | DATE | | | |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

| | | | | QUALITY PLAN | | | | | | | | | | | | PROJECT : Duvha | | | | | |
|---|--|--|--|--------------------|--|--|--|--|---------------------|--|--|--|--|---|--|------------------|--|------|--|---------|--|
| CLIENT : ESKOM DUVHA Unit 3 | | | | 1 = Supplier | | | | | V = Verify | | | | | Quality Plan Reference : Duvha 2009 Rev # : 0 | | | | | | | |
| CLIENT ORDER # : | | | | 2 = Eskom | | | | | H = Hold | | | | | Page # : Page 4 of 6 | | | | | | | |
| ITEM DESCRIPTION : FABRIC FILTER BAGS | | | | 3 = | | | | | W = Witness | | | | | Drawing # : 0.57/48834 Rev. 2 | | | | | | | |
| PRODUCT CODE : | | | | 4 = | | | | | S = Surveillance | | | | | CONTRACT # : | | | | | | | |
| SUPPLIER # : | | | | 5 = | | | | | R = Record | | | | | | | | | | | | |
| | | | | Hold or Witness by | | | | | Inspection Required | | | | | | | | | | | | |
| | | | | Reference Document | | | | | V D S P E M D | | | | | Accept Signature | | Reject Signature | | Date | | Remarks | |
| Op # | | | | 1 2 3 4 5 | | | | | I I T E L A O | | | | | | | | | | | | |
| | | | | | | | | | S M R R O S C | | | | | | | | | | | | |
| | | | | | | | | | N E M N S | | | | | | | | | | | | |
| 5 CONTINUOUS TUBER | | | | MCP | | | | | | | | | | | | | | | | | |
| 5.1 PILOT BAG | | | | | | | | | | | | | | | | | | | | | |
| The very first bag of production to be approved | | | | H H | | | | | X X | | | | | X | | | | | | | |
| At the start of every shift the first tube seamed is sent through the entire manufacturing process and is subjected to critical inspection at every manufacturing stage . | | | | H V | | | | | X X | | | | | X | | | | | | | |
| Should any problems be identified , immediate effective Corrective Action will be taken prior to manufacturing continuing . | | | | | | | | | | | | | | | | | | | | | |
| All foregoing details will be recorded in the CT Diary and the QA Diary . | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| 5.2 IN PROCESS INSPECTION | | | | | | | | | | | | | | | | | | | | | |
| Every tube is inspected by the Operator for : | | | | | | | | | | | | | | | | | | | | | |
| ~ Flat width | | | | Drawing S V | | | | | X | | | | | X | | | | | | | |
| ~ Seam form and stitching | | | | Drawing S V | | | | | X X | | | | | X | | | | | | | |
| ~ Length | | | | Drawing S V | | | | | X | | | | | X | | | | | | | |
| ~ Tube fabric appearance | | | | S V | | | | | X | | | | | | | | | | | | |
| Tubes that pass inspection are stamped with the roll identification # to so signify . | | | | MCP S V | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| 5.3 TOP CUFF | | | | | | | | | | | | | | | | | | | | | |
| Every Top Cuff is inspected by the Operator for : | | | | | | | | | | | | | | | | | | | | | |
| ~ Fabric appearance | | | | S V | | | | | X | | | | | | | | | | | | |
| ~ Seam Form and Stitching | | | | S V | | | | | X X | | | | | | | | | | | | |
| ~ Stitching Dimensions from the edge | | | | S V | | | | | X | | | | | | | | | | | | |
| ~ Stitching Identity Tag | | | | S V | | | | | X | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |
| | | | | | | | | | | | | | | | | | | | | | |

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

[illegible]

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

[illegible]

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.4 DEVIATIONS FROM BAG MATERIAL STANDARD

Based on project specific requirements, the project engineer in consultation with the Senior Consultant – Air Pollution Control and Senior Advisor – Polymers and Filtration may make informed material selections which differ from those in sections 3.1 and 3.2. This may only be done if guarantee requirements are still met and thorough testing of the fabric has been completed.

Eskom has over the years tested a number of fabric configurations which include coated material, self-supporting scrim-less material, finer denier surface blended fabric and alternate fibers etc. The results of these tests are documented in research reports indicating if they are suitable or not. In a number of these instances, these alternate fabrics contain proprietary supplier information and as such cannot be included in the Standard. Should these fabrics be offered as alternates in any tender submission, the offer need to be evaluated on the merits of each submission in consultation with the Senior Consultant – Air Pollution Control and Senior Advisor – Polymers and Filtration.

LIST OF TRIAL BAGS TESTED FOR USE IN ESKOM POWER PLANTS

| Power Station | Bag Description | Purpose | Supplier | Installation Date | Hours | Status |
|-----------------------------|--|---|--------------------|-------------------|--------|---------------------------|
| Medupi Unit 3 | (30) Low Drag PTFE Coated PPS Bags | Chemical Resistance and Air Permeability Consistency | WL Gore | 06/05/2019 | 100 | In Progress |
| Medupi Unit 3 | (27) PPS Fine Fibre Material | PPS Fine Fibre Material | Gutsche | 06/05/2019 | 100 | In Progress |
| Camden Unit 7 | (99) Huvis PPS/PI Bags | Evaluation of New PPS Bagfilter Material | Testori | 01/02/2016 | 20 000 | In Progress (Recommended) |
| Camden Unit 2 | 0 (31) PTFE/PTFE | Evaluation of New Bagfilter Material for High Temperature Application | BWF | 11/09/2013 | 21 351 | Not Recommended |
| Camden Unit 2 | 0 (31) PFB/PTFE Bags | Evaluation of New Bagfilter Material for High Temperature Application | BWF | 11/09/2013 | 21 351 | Not Recommended |
| Camden Unit 2 | 0 (20) PPS/PI Bags | New Supplier Assessment | Filtafelt | 11/09/2013 | 21 351 | Recommended |
| Duvha Unit 1, Cell C | 8 (16) Didom (Pink) Bags | New Fibre Assessment | Beier Envirotech | 26/05/2013 | 18 000 | Not Recommended |
| Duvha Unit 1, Cell C | 14 (18) PPS Super Novates Coated Bags | Improved Coating Assessment | Testori | 26/05/2013 | 18 000 | In Progress (Cancelled) |
| Hendrina Unit 1 | 18 PPS & 18 PPS/PI Bags (36) | New Supplier Assessment | Tamfelt (Metso) | 10/07/2012 | 15 000 | In Progress (Recommended) |
| Hendrina Unit 7 | 10 (26) China PPS Bags | China PPS Assessment | BWF | 15/04/2012 | 14 000 | In Progress (Plant Risk) |
| Hendrina Unit 5 | 0 (4) PAN Tectus Bags by How den | Shrinkage reduction | Andrew Webron | 17/01/2011 | 18 000 | In Progress (Plant Risk) |
| Hendrina Unit 5 | 30 (60) Tectus PAN Bags by Clear Edge | Shrinkage reduction | Andrew Webron | 17/01/2011 | 18 000 | In Progress (Plant Risk) |
| Hendrina Unit 5 | 10 (18) Red Bags by BWF | Shrinkage reduction | BWF | 17/01/2011 | 18 000 | Not Recommended |
| Hendrina Unit 8 | 14 (36) self-supporting PPS Bags | Improved filtration efficiency at reduced cost | Andrew Webron | 25/04/2008 | 40 500 | Recommended |
| Majuba Unit 5 Cell 1.2 | 0 (6) PAN Tectus/polyimide (PI) Bags | Shrinkage reduction | Andrew Webron | 09/09/2010 | 18 000 | Recommended |
| Majuba Unit 5 Cell 1.2 | 60 (70) PAN (Dralon)/PI/AKSA Bags | Ricem alternative/shrinkage reduction | Gutsche/Clear Edge | 09/09/2010 | 18 000 | Recommended |
| Majuba Unit 5 Cell 1.2 | 0 (34) Gutsche PAN/PI Bags (AKSA) | Shrinkage/filtration efficiency | Gutsche/Clear Edge | 09/09/2010 | 18 000 | Recommended |
| Majuba Unit 5 Cell 1.2 | 0 (21) Gutsche PAN Bags (AKSA) | Shrinkage/filtration efficiency | Gutsche/Clear Edge | 09/09/2010 | 18 000 | Recommended |
| Duvha Unit 2 | 0 (21) PPS/PI Bags | New bag supplier evaluation | Stokto/Kayser | 28/11/2008 | 35 000 | Not Recommended |
| Majuba Unit 3 Cell 2.3 | 0 (16) PAN Ricem Bags | Shrinkage reduction | Testori | 13/02/2009 | 25 000 | N/A |
| Majuba Unit 3 Cell 2.3 | 0 (16) PAN Ricem Bags | Shrinkage reduction | Testori | 13/02/2009 | 25 000 | N/A |
| Majuba Unit 3 Cell 2.3 | 0 (19) iron oxide treated Dolanit Bags | Shrinkage reduction | BWF | 13/02/2009 | 25 000 | Not Recommended |
| Majuba Unit 4 Cell 2.4 | 0 (73) special heat treated Dolanit Bags | Shrinkage reduction | Andrew Webron | 17/09/2009 | 25 000 | Not Recommended |
| Duvha Unit 1, Cell A | 0 (18) PPS Bags with Novates (PU) coating | Improved chemical resistance/filtration efficiency | Testori | 18/01/2008 | 35 212 | Recommended |
| Duvha Unit 1, Cell A | 9 Light Scrim (130), 9 Heavy Scrim 170, 9 High Heat Set PAN (27) | Accelerated Test on PAN, Heat Set Test for Supplier | Beier Envirotech | 24/05/2007 | 18 000 | N/A, Supplier Test |
| Duvha Unit 2 Cell D | 0 (1) Red Bag | Accelerated Test on Red Bag | Gutsche | 9/02/2006 | 19 000 | Not Recommended |
| Majuba Unit 6 Cell 1.2 | 0 (4) Red Bags | Shrinkage reduction | Gutsche | 01/03/2006 | 26 000 | Not Recommended |
| Majuba Unit 5 Cell 2.4 | 0 (62) Red Bags | Shrinkage reduction | Beier Envirotech | 01/09/2006 | 25 000 | Not Recommended |
| Majuba Unit 3 Cell 1.2 | 0 (3) Red Bags | Shrinkage reduction | Gutsche | 15/06/2005 | 26 000 | Not Recommended |
| Hendrina Unit 4 (LHC & RHC) | 0 (4) Red Bags | Shrinkage reduction | Gutsche | 31/12/2005 | 26 000 | Not Recommended |

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

4.5 PRE-COATING OF BAGS

All complete cells/compartments or units that are fully rebagged must be coated with hydrated lime before the cells/compartments are put into service.

The minimum amount of hydrated lime required is based on 1 kg per 1 m² of fabric.

High Calcium Hydrated Lime Specifications:

| Chemical Properties | Average (%) | Min. (%) | Max. (%) |
|--|---------------------------|----------|----------|
| Free Calcium Oxide (CaO) | 0.16 | - | 1.00 |
| Magnesium Oxide (MgO) | 1.01 | - | 1.20 |
| Silica | 0.50 | - | 0.98 |
| Ferric Oxide (Fe ₂ O ₃) | 0.15 | - | 0.60 |
| Alumina (Al ₂ O ₃) | 0.08 | - | 0.35 |
| Calcium Hydroxide (CaOH ₂) | 94.8 | 90.0 | - |
| Carbon Dioxide (CO ₂) | 0.60 | - | 1.5 |
| Free Moisture (H ₂ O) | 0.64 | 0 | 2.00 |
| | | | |
| Colour / Texture | Light Brown / Fine Powder | | |

High Calcium Hydrated Lime Particle Size:

| Size Parameter | Typical | Units |
|----------------|---------|-------|
| < 850 micron | 100 | % |
| < 300 micron | 99.5 | % |
| < 100 micron | 99.0 | % |
| < 75 micron | 85 | % |

4.6 SPARE BAGS

Stations are advised to keep sufficient stock of spare bags to replace failed bags that occur during the course of operation. The recommended minimum stock level is 3% of the total installed number of bags per station and the material should comply with the standards detailed in this document.

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

5. AUTHORISATION

This document has been seen and accepted by:

| Name | Designation |
|-----------------|---|
| KB Naicker | Senior Manager (Acting) – Production Engineering Integration (Group Technology) |
| H Grobbelaar | Senior Consultant – Air Pollution Control (Group Technology) |
| RA Van Rensburg | Corporate Consultant – Air Pollution Control (Group Technology) |
| N Haripersad | Resources & Integrity Manager – CCECT, ERID (Sustainability) |
| I Phiri | Senior Advisor – Polymers & Filtration, ERID (Sustainability) |
| F Makananise | Manager – Condition Monitoring, Polymers & Filtration, ERID (Sustainability) |
| T Mokgatle | Engineering Manager – Arnot (Generation) |
| M Mathabatha | Engineering Manager – Camden (Generation) |
| N Toerien | Engineering Manager – Duvha (Generation) |
| T Montja | Engineering Manager – Grootvlei (Generation) |
| M Raphasha | Engineering Manager – Hendrina (Generation) |
| V Boya | Engineering Manager – Majuba (Generation) |
| J Mkhathswa | Engineering Manager – Medupi (Generation) |
| N Mhlungu | Engineering Manager – Kusile (Generation) |
| P Mhlongu | Supplier Assessment Advisor – Quality Management (Group Technology) |
| J Mchunu | Project Manager – FFP Bags, |
| S Peta | Boiler Auxiliary Manager – Boiler Auxiliary Group (Group Technology) |
| EM Patel | SCOT: Particulate Care Group Chairperson |
| Y Singh | SCOT: AQC SC Chairperson |
| S Govender | General Manager Plant Engineering (Acting) |

6. REVISIONS

| Date | Rev. | Compiler | Remarks |
|----------------|------|------------|--|
| November 2012 | 0 | E.M. Patel | Draft to Replace 474-274 |
| August 2013 | 1 | E.M. Patel | Final Document for Authorisation |
| December 2015 | 1.3 | E.M. Patel | General Update |
| December 2015 | 1.4 | E.M. Patel | Draft Document for Comments Review |
| February 2016 | 2 | E.M. Patel | Final Document for Authorisation and Publication |
| July 2019 | 2.1 | E.M. Patel | Document Revision |
| September 2019 | 2.2 | E.M. Patel | Draft Document for Comments Review |
| October 2019 | 2.3 | E.M. Patel | Updated Final Draft after Comments Review |
| October 2019 | 3 | E.M. Patel | Final Document for Authorisation and Publication |

7. DEVELOPMENT TEAM

The following people were involved in the development of this document:

- Ebrahim Patel

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.

- Hendre Grobbelaar
- Robbie Van Rensburg
- Nomathemba Mpulo
- Charlene Naicker
- Moloko Radipabe
- John Ramaboea
- Luyanda Mvulane
- Nthabiseng Tsosane
- Mzwandile Gcaleka
- Pieter Swart
- Jeanne Fourie
- Riana Nieuwoudt
- Hendrik Van Riel
- Irish Phiri
- Spinola Baloyi

8. ACKNOWLEDGEMENTS

None

CONTROLLED DISCLOSURE

When downloaded from the EDMS, this document is uncontrolled and the responsibility rests with the user to ensure it is in line with the authorised version on the system.